

Magnetic Excitations of the Diagonal Incommensurate Phase in Lightly-Doped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$

M. Matsuda,¹ M. Fujita,² S. Wakimoto,¹ J. A. Fernandez-Baca,³ J. M. Tranquada,⁴ and K. Yamada²

¹Quantum Beam Science Directorate, Japan Atomic Energy Agency, Tokai, Ibaraki 319-1195, Japan

²Institute for Materials Research, Tohoku University, Katahira, Sendai 980-8577, Japan

³Neutron Scattering Science Division, Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

⁴Brookhaven National Laboratory, Upton, New York 11973, USA

(Dated: June 25, 2021)

We present inelastic neutron scattering experiments on a single-domain crystal of lightly-doped $\text{La}_{1.96}\text{Sr}_{0.04}\text{CuO}_4$. We find that the magnetic excitation spectrum in this insulating phase with a diagonal incommensurate spin modulation is remarkably similar to that in the superconducting regime, where the spin modulation is bond parallel. In particular, we find that the dispersion slope at low energy is essentially independent of doping and temperature over a significant range. The energy at which the excitations cross the commensurate antiferromagnetic wave vector increases roughly linearly with doping through the underdoped regime.

PACS numbers: 74.72.Dn, 75.40.Gb

Superconductivity in the cuprates is obtained by doping holes into a parent antiferromagnetic insulator. How the transition occurs from antiferromagnetic to superconducting ground states as a function of doping remains a controversial issue. In the case of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO), the commensurate antiferromagnetic order disappears at $x = 0.02$, while superconductivity appears for $x \gtrsim 0.055$; the region in between is often called the “spin-glass” phase [1]. Neutron scattering studies have shown that, at low temperatures ($T < T_{\text{el}} \sim 20$ K), magnetic ordering is indicated by the appearance of incommensurate elastic peaks split about the antiferromagnetic wave vector, \mathbf{Q}_{AF} [2, 3]. The corresponding spin modulation occurs within the CuO_2 planes along a direction at 45° to the Cu-O bonds; in fact, it has a unique orientation with respect to the orthorhombic axes [4]. The magnetic incommensurability rotates to parallel to the Cu-O bond direction with the onset of superconductivity at $x \sim 0.055$. The change in character of the magnetic correlations at the onset of superconductivity is of particular interest, especially in light of recent evidence for a vortex-liquid state extending from the superconducting regime down to $x \approx 0.03$ [5].

Here we present an inelastic neutron scattering study of the spin dynamics in LSCO with $x = 0.04$, in the middle of the spin-glass regime. Despite the rotated incommensurability, we find that the spectrum is consistent with the “hour-glass” dispersion observed in superconducting LSCO [6, 7, 8] (and also in $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ [9, 10, 11, 12, 13]). Even at $T \gg T_{\text{el}}$, there is a strong anisotropy of the low-energy fluctuations, consistent with the nematic-like response recently reported for $\text{YBa}_2\text{Cu}_3\text{O}_{6.45}$ [14, 15]. Furthermore, the effective velocity of the low-energy excitations is approximately independent of energy, so that the energy, E_{cross} , at which the low-energy excitations cross \mathbf{Q}_{AF} scales linearly with doping, following the elastic limit of the mag-

netic incommensurability. The lack of variation of the spin-fluctuation velocity is reminiscent of the doping-independence of the Fermi velocity observed in photoemission studies [16]; however, we can rule out a spin-density-wave instability as the source of the low-energy magnetic correlations, because the magnitude of $2k_{\text{F}}$ (twice the Fermi wave vector) measured by photoemission [17] is inconsistent with the magnetic wave vector. At energies above E_{cross} , the magnetic excitations are consistent with the effective antiferromagnetic dispersion previously observed in LSCO with $x = 0.05$ [18]. This supports the concept that the magnetic excitations evolve directly from the antiferromagnetic insulator.

The main focus of this work involves a single crystal of $\text{La}_{1.96}\text{Sr}_{0.04}\text{CuO}_4$; however, we will also show some results for $\text{La}_{1.95}\text{Sr}_{0.05}\text{Cu}_{0.97}\text{Zn}_{0.03}\text{O}_4$ (LSCZO), which is quite similar [19]. Both crystals were grown by the traveling solvent floating zone method and have dimensions of $\sim 6 \phi \times 25 \text{ mm}^3$. Each crystal contains essentially a single domain of the low-temperature orthorhombic structure, with lattice parameters $a = 5.34 \text{ \AA}$ and $b = 5.42 \text{ \AA}$ for the pure LSCO crystal at low temperature. The a and b axes are at 45° to the Cu-O bonds. In this coordinate system, $\mathbf{Q}_{\text{AF}} = (100), (010)$, in reciprocal lattice units, $(2\pi/a, 2\pi/b, 2\pi/c)$. The incommensurate magnetic peaks are split uniquely along \mathbf{b}^* by an amount ϵ .

The elastic magnetic scattering was characterized on the cold triple-axis spectrometer LTAS at the Japanese Research Reactor (JRR-3) of the Japan Atomic Energy Agency (JAEA). Neutrons with an energy of 5 meV were used, together with a horizontal collimator sequence of guide- $80'$ -S- $80'$ - $80'$; contamination from higher-order beams was effectively eliminated using Be filters. The LSCO sample yielded incommensurate peaks with $\epsilon = 0.0513(7)$ rlu for $T \lesssim 20$ K, with a Lorentzian line width of $\kappa = 0.04 \text{ \AA}^{-1}$. For LSCZO, $\epsilon = 0.0543$ rlu [19].

The inelastic scattering measurements on LSCO were

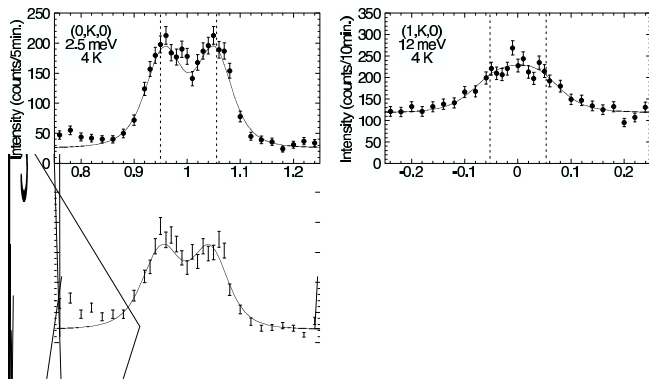


FIG. 1: Neutron inelastic scans along $(0, K, 0)$, $(1, K, 0)$, or $(2, K, 0)$ in $\text{La}_{1.96}\text{Sr}_{0.04}\text{CuO}_4$. The solid lines are the results of fits as discussed in the text. The broken lines represent the peak positions observed at $\hbar\omega = 0$ meV. The measurements were performed on TAS-2 for $\hbar\omega \leq 12$ meV and on TAS-1 for $\hbar\omega \geq 15$ meV.

performed on the thermal triple-axis spectrometers TAS-1 and TAS-2 at JRR-3 with a fixed final neutron energy, E_f , of 13.7 meV. The horizontal collimator sequences were open- 80° -S- 80° - 80° on TAS-1 and guide- 80° -S- 80° -open on TAS-2. For LSCZO, the measurements were performed on the thermal triple-axis spectrometer HB-1 at the High Flux Isotope Reactor (HFIR), Oak Ridge National Laboratory. The measurement conditions were $E_f = 14.7$ meV, horizontal collimations of 48° - 60° -S- 80° - 240° . Pyrolytic graphite (PG) filters were used to suppress higher harmonics. The single crystals were oriented in the $(HK0)$ scattering plane and were mounted in a closed-cycle He gas refrigerator.

Figure 1 shows the typical neutron inelastic scattering spectra between 2.5 meV and 30 meV in LSCO ($x = 0.04$) measured at low temperature along the modulation direction. At energies of 4 meV and below, the two peak structure is clear. With increasing energy, the peak separation becomes smaller and the peak width also becomes broadened. We have confirmed that the peak broadening corresponds to the resolution effect. The solid lines in Fig. 1 are the results of fits of a convolution of the resolution function with two 2-dimensional (2D) squared Lorentzians. In the fitting, the linewidth (κ) of each peak, which corresponds to the effective inverse

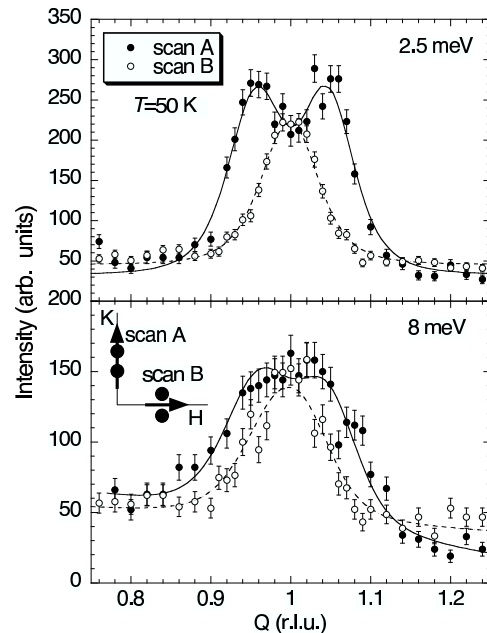
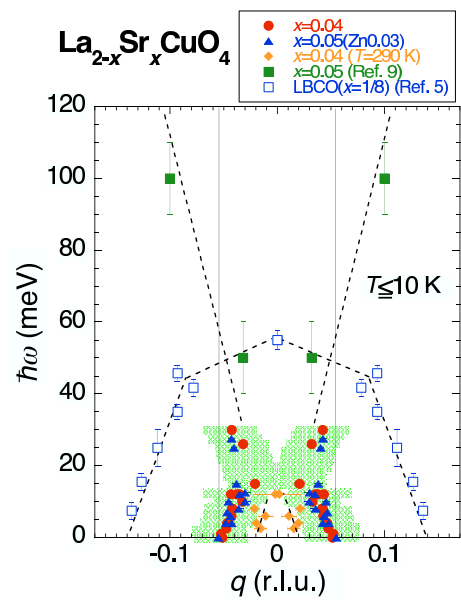


FIG. 2: Scans measured parallel (scan A) and perpendicular (scan B) to the incommensurate wave vector, as indicated in the inset, for energies of 2.5 and 8 meV at $T = 50$ K. The particular positions for the scans were chosen to optimize the resolution.

correlation length, is assumed to be isotropic in the a - b plane and fixed at the value determined from the elastic scattering (0.04 \AA^{-1}). This model reproduces the observed spectra reasonably well for all measured energies ($2.5 \leq \hbar\omega \leq 30$ meV). The analysis indicates that the peak separation (2ϵ) decreases towards zero as $\hbar\omega$ is raised to 15 meV. Since phonon scattering contaminates the magnetic signal in the range of $15 < \hbar\omega < 25$ meV, we could not clarify the magnetic spectra in that region. The peak separation appears to grow for $\hbar\omega > 25$ meV. The Q -integrated intensity decreases monotonically with increasing energy. This behavior is consistent with that observed in LSCO with $x = 0.05$ [18]; however, it is distinct from the reported behavior in LSCO with $x = 0.16$ [7] and in $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$ [6], where the intensity peaks at finite energy.

The anisotropy of the scattering, measured parallel and perpendicular to the incommensurate peaks, is shown in Fig. 2 for $T = 50 \text{ K} \gg T_{el}$, where there is no static order. This is to illustrate that the character of the low-energy spin correlations does not depend on whether there is a static component. As noted in the introduction, this anisotropy looks very similar to that found recently in $\text{YBa}_2\text{Cu}_3\text{O}_{6.45}$ [14] and consistent with expectations for a nematic electronic state [15]. (Of course, in both of these cases, there is already a reduction from 4-fold symmetry due to the crystal structure.) It is also of interest to consider the 2D distribution of intensity at 25 meV and above; however, resolution effects prevented any defini-



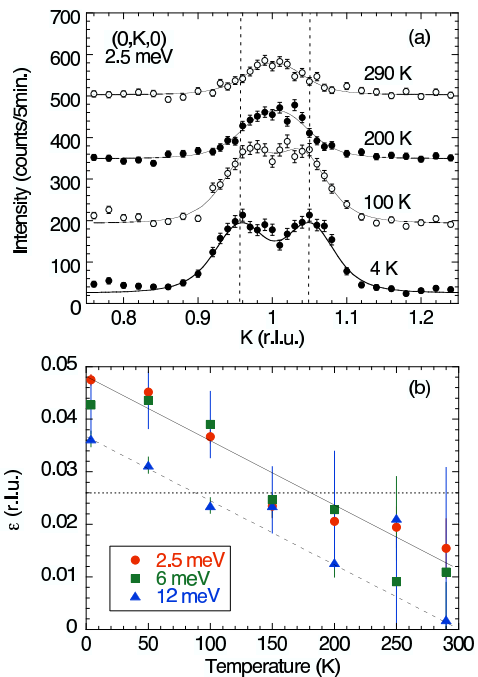


FIG. 5: (Color online) (a) Temperature dependence of the magnetic excitation spectra at 2.5 meV. Successive scans have been displaced vertically by 150 counts for clarity. The solid lines are the results of fits of a convolution of the resolution function with two 2D squared Lorentzians. The broken lines represent the peak positions at 4 K. (b) Temperature dependence of the incommensurability (ϵ) at 2.5, 6, and 12 meV in $\text{La}_{1.96}\text{Sr}_{0.04}\text{CuO}_4$. The solid and broken lines are visual guides for the data. The dotted horizontal line shows the peak width (HWHM). Two peaks can hardly be resolved when ϵ becomes much smaller than this value.

In terms of a stripe picture, the dominant magnetic interaction would be superexchange within locally antiferromagnetic domains. There is still a challenge to understand why the dispersion of the low-energy excitations is not significantly affected by the rotation in stripe orientation. One possibility suggested by Granath [30] is that a diagonal stripe might consist of a staircase pattern of bond-parallel stripes. He found that such a pattern seemed necessary in order to obtain consistency with the photoemission experiments [17]. We note that the magnetic spectrum is distinct from that observed in the insulating diagonal stripe phase of $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ [31, 32]. Also, $E_{\text{cross}} \sim x$ is a stronger variation than predicted by the stripe-phase calculations of Seibold and Lorenzana [33]. Thus, while our results may be phenomenologically consistent with stripe correlations, improvements in theoretical models are needed.

We would like to thank T. Tohyama and Y. Koike for stimulating discussions. This study was supported in part by the U.S.-Japan Cooperative Program on Neutron Scattering and by a Grant-in-Aid for Scientific Re-

search from the MEXT of Japan. Work at Oak Ridge National Laboratory and Brookhaven National Laboratory was supported by the U.S. Department of Energy's Office of Science under Contract Nos. DE-AC05-00OR22725A and DE-AC02-98CH10886, respectively.

-
- [1] R. J. Birgeneau, C. Stock, J. M. Tranquada, and K. Yamada, *J. Phys. Soc. Jpn.* **75**, 111003 (2006).
 - [2] M. Fujita, H. Goka, K. Yamada, and M. Matsuda, *Phys. Rev. Lett.* **88**, 167008 (2002).
 - [3] S. Wakimoto *et al.*, *Phys. Rev. B* **60**, R769 (1999).
 - [4] S. Wakimoto *et al.*, *Phys. Rev. B* **61**, 3699 (2000).
 - [5] L. Li, J. G. Checkelsky, S. Komiyama, Y. Ando, and N. P. Ong, *Nat. Phys.* **3**, 311 (2007).
 - [6] J. M. Tranquada *et al.*, *Nature* **429**, 534 (2004).
 - [7] B. Vignolle *et al.*, *Nature Phys.* **3**, 163 (2007).
 - [8] M. Kofu, T. Yokoo, F. Trouw, and K. Yamada (2007), URL <http://arXiv:0710.5766>.
 - [9] M. Arai *et al.*, *Phys. Rev. Lett.* **83**, 608 (1999).
 - [10] S. M. Hayden, H. A. Mook, P. Dai, T. G. Perring, and F. Doğan, *Nature* **429**, 531 (2004).
 - [11] D. Reznik *et al.*, *Phys. Rev. Lett.* **93**, 207003 (2004).
 - [12] C. Stock *et al.*, *Phys. Rev. B* **71**, 024522 (2005).
 - [13] V. Hinkov *et al.*, *Nature Phys.* **3**, 780 (2007).
 - [14] V. Hinkov, D. Haug, B. Fauqué, P. Bourges, Y. Sidis, A. Ivanov, C. Bernhard, C. T. Lin, and B. Keimer (2007), preprint.
 - [15] S. A. Kivelson, E. Fradkin, and V. J. Emery, *Nature* **393**, 550 (1998).
 - [16] X. J. Zhou *et al.*, *Nature* **423**, 398 (2003).
 - [17] T. Yoshida *et al.*, *Phys. Rev. B* **74**, 224510 (2006).
 - [18] H. Goka *et al.*, *Physica C* **388–389**, 239 (2003).
 - [19] M. Matsuda, M. Fujita, and K. Yamada, *Phys. Rev. B* **73**, 140503(R) (2006).
 - [20] M. Matsuda *et al.*, *Phys. Rev. B* **61**, 4326 (2000).
 - [21] H. Hiraka *et al.*, *J. Phys. Soc. Japan* **70**, 853 (2001).
 - [22] C. D. Batista, G. Ortiz, and A. V. Balatsky, *Phys. Rev. B* **64**, 172508 (2001).
 - [23] M. Dumm, S. Komiyama, Y. Ando, and D. N. Basov, *Phys. Rev. Lett.* **91**, 077004 (2003).
 - [24] A. Luscher, A. I. Milstein, and O. P. Sushkov, *Phys. Rev. B* **75**, 235120 (2007).
 - [25] N. Hasselmann, A. H. Castro Neto, and C. M. Smith, *Phys. Rev. B* **69**, 014424 (2004).
 - [26] M. Berciu and S. John, *Phys. Rev. B* **69**, 224515 (2004).
 - [27] V. Juricic, M. B. Silva Neto, and C. M. Smith, *Phys. Rev. Lett.* **96**, 077004 (2006).
 - [28] C. Brugger, C. P. Hofmann, F. Kampfer, M. Pepe, and U.-J. Wiese, *Phys. Rev. B* **75**, 014421 (2007).
 - [29] J. Friedel, *J. Phys. Condens. Matter* **1**, 7757 (1989).
 - [30] M. Granath, *Phys. Rev. B* **69**, 214433 (2004).
 - [31] P. Bourges, Y. Sidis, M. Braden, K. Nakajima, and J. M. Tranquada, *Phys. Rev. Lett.* **90**, 147202 (2003).
 - [32] H. Woo *et al.*, *Phys. Rev. B* **72**, 064437 (2005).
 - [33] G. Seibold and J. Lorenzana, *Phys. Rev. B* **73**, 144515 (2006).