

March 31 2021

Superconductivity above 200K Observed in Superhydrides of Calcium

Z.W.Li, X.He, C.L.Zhang, S.J.Zhang, S. M.Feng, X.C.Wang, R.C.Yu, C.Q.Jin

Institute of Physics Chinese Academy of Sciences(IOPCAS), Beijing, China

Abstract

The calcium superhydrides are synthesized at high pressure of 160 GPa & high temperature. Superconductivity with T_c onset about 210 K is realized in thus obtained hydrogen rich calcium compounds at high pressure. The critical magnetic field $H_c(0)$ is estimated to be ~ 169 T in the Ginzburg Landau model.

CQJ: Jin@iphy.ac.cn;

XCW: wangxiancheng@iphy.ac.cn

Introduction

The superhydrides compounds received growing attentions recently because of the high temperature superconductivity reported in the system¹⁻⁸. It was suggested superhydrides are likely to be a step toward metallic hydrogen since the “chemically precompressed” hydrogen in the superhydrides can decrease the critical pressure required for the metallization^{1,8}. Sulfur hydrides are one of examples, in which the high T_c superconductivity was reported both theoretically & experimentally at Megbar level pressures^{5,2}. In addition rare earth superhydrides and alkali earth superhydrides are theoretically predicted to possess high temperature superconductivity at high pressures^{9,10,11}. Those metal superhydrides favor to form clathrate like cage structures at high pressure where the metal ions are located in the center of the H-clathrats and act as electron donor. The occupation of the unfilled anti-bonding σ^* orbitals of the H_2 molecules by the electrons from the metal ions would dissociate the H_2 molecules to form H clathrats¹⁰. Although the superconductivity above 200 K was reported in rare earth superhydrides such as LaH_{10} ^{3,4}, there is no experimental observations for superconductivity above 200 K so far in alkaline earth superhydrides, in spite of the superconductivity was reported in barium hydrides¹². Here, we report the experimental observation of high T_c superconductivity in calcium superhydrides synthesized at high pressure and high temperature conditions. The SC with $T_c \sim 210$ K at 160 GPa was observed in the calcium superhydrides system based onsite high pressure resistance measurements.

Experiments

The calcium hydrides are synthesized using diamond anvil cell following the procedure described in Ref.13. The diamond anvils with culet diameter of 100 μm beveled to 300 μm are used for the experiments. The Pt foils with the thickness of 0.5 μm deposited on the surface of the culet of diamond anvil are used as the inner electrodes. The calcium specimen with a shape of 30 $\mu m \times 30 \mu m$ and the thickness of 2 μm stacks on the inner electrodes. The gold wire of 18 micrometers diameter was used as the outside electrodes. They contact closely each other. The prepressed stainless steel with a thickness of 20 μm serves as gasket. A hole drilled at the center of gasket was filled with fine cubic boron nitride (cBN) powder mixed with epoxy. A center hole of 70 μm in diameter was drilled to serve as the sample chamber. The ammonia borane (AB) filled in the sample chamber was used as the hydridezer to provide hydrogen during chemical reaction⁴. Pressure was calibrated by the shift of the first order Raman edge frequency from the cutlet of diamond^{14,15}. The specimen was heated at 160 GPa for the by a laser beam with light spot of 5 μm in diameter at a laser power of 20 W. The temperature was fitted by collecting black body irradiation

spectra from specimen. The temperature is thus estimated to be ~2000K at 160 GPa. The specimen was quenched from high temperature while keep the pressure at 160 GPa(the maximum pressure without broken the culet in our experiments). The diamond anvil cell was then put into a MagLab system to perform the electric conductivity measurements. The Van der Pauw method was adopted to the in situ high pressure resistance measurements with 1 mA applied current. The MagLab system can provide synergetic extreme environments with temperatures from 300 K to 1.5 K and a magnetic field up to 9 T¹⁶⁻¹⁸.

Results & Discussions

Fig. 1(a) displays the image of the sample assembly. The dotted red square is the sample shape and the four gray dotted regions are the inner electrodes. Fig. 1(b) shows the measurements of resistance as function of temperature at 160 GPa for two synthesized samples with different profile. The resistance curves almost coincide for the cooling and warming cycles as shown in Fig.1(b). The resistance approach to zero at low temperature suggesting that superconducting transitions take place in the calcium superhydrides. The inset of Fig. 1(b) displays the enlarge view of resistance curve around the transition region measured for sample 1. Here the T_c onset of 210 K is estimated from the upturn point of the derivative of resistance over temperature as shown in the inset of Fig.1(b). The value of experimentally observed 210K T_c is comparable to that of theoretical prediction for the calcium hydride of CaH₆ with a clathrate like structure¹⁰. However, it is also observed that there are several drop steps such as at ~160 K and ~180 K, respectively as shown in Fig.1(b). They are attributed to possible phases with different hydrogen amount in the synthesized calcium superhydrides. These superconducting phases synthesized at 160 GPa are not discussed in the previous published calculations.

To confirm the superconducting transition, we performed the resistance measurements by application of magnetic fields as shown in Fig. 2. It is seen that the whole transition curves shift to low temperature with the critical temperature gradually suppressed by the applied field, in consistent with the nature of superconductivity. The curves become broaden from the transition temperatures at the kinks as indicated by the arrows, supporting the speculations that the kinks are from the superconducting transitions. To estimate the upper critical field of the 210K phase, the T_c versus applied magnetic field is correlated. The critical field as a function of temperature is plotted as Fig. 3. From the inset of Fig. 3, one can see that the critical field increases linearly with the decrease of temperature at low magnetic fields region. The Ginzburg Landau (GL) formula of $H_{c2}(T) = H_{c2}(0)(1 - (T/T_c)^2)$ is used to estimate the upper critical field at zero temperature. As shown in Fig 3, the fitting of

the $H_{c2}(T)$ by the GL formula gives the value of $H_{c2}(0)\sim 169$ T.

Summary

We successfully synthesized superhydrides of calcium at high pressure and high temperature conditions. The sample shows superconducting transition above 210 K at 160 GPa. The upper critical field $\mu_0 H_{c2}(0)$ for the phase is estimated to be 169T.

Acknowledgments:

The work is supported by NSF, MOST & CAS through research projects. We are grateful to Prof. J. G. Cheng, J.P.Hu & L. Yu for the discussions. We thank Prof. T. Xiang, S.S. Xie, & Z. X. Zhao for the consistent encouragements.

References:

1. N. W. Ashcroft, "Hydrogen dominant metallic alloys: High temperature superconductors?," *Phys. Rev. Lett.* **92** (18), 187002 (2004).
2. A. P. Drozdov, M. I. Eremets, I. A. Troyan, V. Ksenofontov, and S. I. Shylin, "Conventional superconductivity at 203 kelvin at high pressures in the sulfur hydride system," *Nature* **525** (7567), 73 (2015).
3. A. P. Drozdov, P. P. Kong, V. S. Minkov, S. P. Besedin, M. A. Kuzovnikov, S. Mozaffari, L. Balicas, F. F. Balakirev, D. E. Graf, V. B. Prakapenka, E. Greenberg, D. A. Knyazev, M. Tkacz, and M. I. Eremets, "Superconductivity at 250 K in lanthanum hydride under high pressures," *Nature* **569** (7757), 528 (2019).
4. M. Somayazulu, M. Ahart, A. K. Mishra, Z. M. Geballe, M. Baldini, Y. Meng, V. V. Struzhkin & R. J. Hemley, "Evidence for Superconductivity above 260 K in Lanthanum Superhydride at Megabar Pressures", *Phys. Rev. Lett.* **122**, 27001 (2019).
5. D. F. Duan, Y. X. Liu, F. B. Tian, D. Li, X. L. Huang, Z. L. Zhao, H. Y. Yu, B. B. Liu, W. J. Tian, and T. Cui, "Pressure-induced metallization of dense (H₂S)₂H-2 with high-T_c superconductivity," *Sci. Rep.* **4**, 6968 (2014);
6. F. Hong, L. X. Yang, P. F. Shan, P. T. Yang, Z. Y. Liu, J. P. Sun, Y. Y. Yin, X. H. Yu, J. G. Cheng, and Z. X. Zhao, "Superconductivity of Lanthanum Superhydride Investigated Using the Standard Four-Probe Configuration under High Pressures," *Chin. Phys. Lett.* **37** (10), 107401 (2020).
7. F. Hong, P. F. Shan, L. X. Yang, B. B. Yue, P. T. Yang, Z. Y. Liu, J. P. Sun, J. H.

- Dai, H. Yu, Y. Y. Yin, X. H. Yu, J. G. Cheng, and Z. X. Zhao, "Superconductivity at ~ 70 K in Tin Hydride SnH_x under High Pressure", ArXiv:2101.02846, (2021).
8. J. A. Xu and Z. W. Zhu, "Metallic Hydrogen," *Physics* 6(in Chinese), 296 (1977).
 9. H. Y. Liu, I. I. Naumov, R. Hoffmann, N. W. Ashcroft, and R. J. Hemley, "Potential high-T-c superconducting lanthanum and yttrium hydrides at high pressure," *Proc Natl Acad Sci U S A/ PNAS* 114 (27), 6990-6995 (2017).
 10. F. Peng, Y. Sun, C. J. Pickard, R. J. Needs, Q. Wu, and Y. M. Ma, "Hydrogen Clathrate Structures in Rare Earth Hydrides at High Pressures: Possible Route to Room-Temperature Superconductivity," *Phys. Rev. Lett.* 119 (10), 107001 (2017).
 11. H. Wang, J. S. Tse, K. Tanaka, T. Iitaka, and Y. M. Ma, "Superconductive sodalite-like clathrate calcium hydride at high pressures," *Proc Natl Acad Sci U S A/ PNAS* 109 (17), 6463-6466 (2012).
 12. W. Chen, D. V. Semenok, A. G. Kvashnin, X. Huang, I. A. Kruglov, M. Galasso, H. Song, D. Duan, A. F. Goncharov, V. B. Prakapenka, A. R. Oganov & T. Cui, "Synthesis of molecular metallic barium superhydride: pseudocubic BaH_{12} ", *Nat. Commun.* 12, 273 (2021).
 13. Y. T. Jia, X. He, S. M. Feng, S. J. Zhang, C. L. Zhang, C. W. Ren, X. C. Wang, and C. Q. Jin, "A Combinatory Package for Diamond Anvil Cell Experiments," *Crystals* 10 (12), 1116 (2020).
 14. Akahama, Y. and H. Kawamura, Pressure calibration of diamond anvil Raman gauge to 310GPa. *Journal of Applied Physics* 100, 43516 (2006).
 15. D. Mao RMPMao, H.K.; Xu, J.; Bell, P.M. Calibration of the ruby pressure gauge to 800 kbar under quasi-hydrostatic conditions. *J. Geophys. Res. Solid Earth* 91, 4673–4676 (1986).
 16. L. X. Yang, J. G. Zhao, Y. Yu, F. Y. Li, R. C. Yu, and C. Q. Jin, "Metallization of Cu_3N semiconductor under high pressure," *Chin. Phys. Lett.* 23, 426 (2006);
 17. S. J. Zhang, X. C. Wang, R. Sammynaiken, J. S. Tse, L. X. Yang, Z. Li, Q. Q. Liu, S. Desgreniers, Y. Yao, H. Z. Liu, and C. Q. Jin, "Effect of pressure on the iron arsenide superconductor Li_xFeAs ($x=0.8,1.0,1.1$)," *Phys. Rev. B* 80 (1), 14506 (2009).
 18. J. L. Zhang, S. J. Zhang, H. M. Weng, W. Zhang, L. X. Yang, Q. Q. Liu, S. M. Feng, X. C. Wang, R. C. Yu, L. Z. Cao, L. Wang, W. G. Yang, H. Z. Liu, W. Y. Zhao, S. C. Zhang, X. Dai, Z. Fang, and C. Q. Jin, "Pressure-induced superconductivity in topological parent compound Bi_2Te_3 ," *Proc Natl Acad Sci U S A/ PNAS* 108 (1), 24(2011);

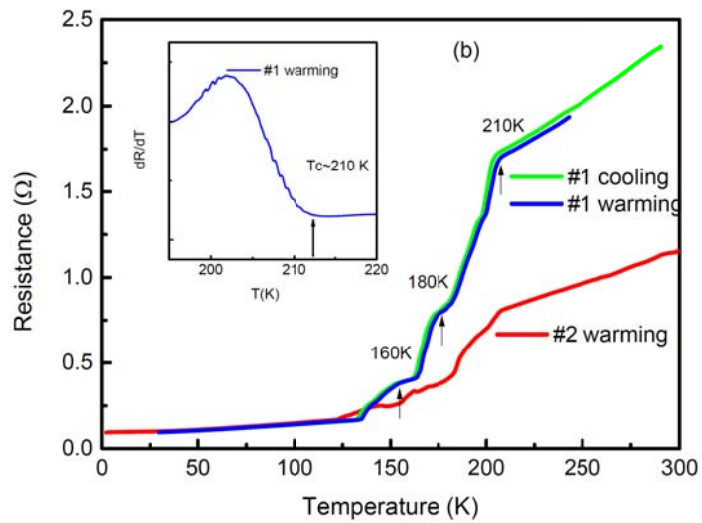
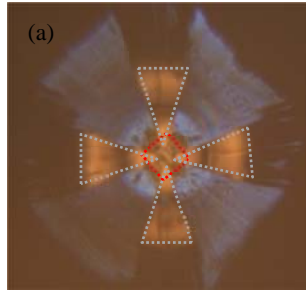


Fig. 1 (a) The image of the specimen assembly after laser heating at 160 GPa. (b) The temperature dependence of resistance $R(T)$ measured under 160 GPa for two samples. The steps in the transition region imply there might be phases with different hydrogen amount in the synthesized calcium superhydrides. The inset is the enlarged view of the derivative of resistance over temperature dR/dT where the $\sim 210\text{K}$ T_c onset is determined as the upturn point.

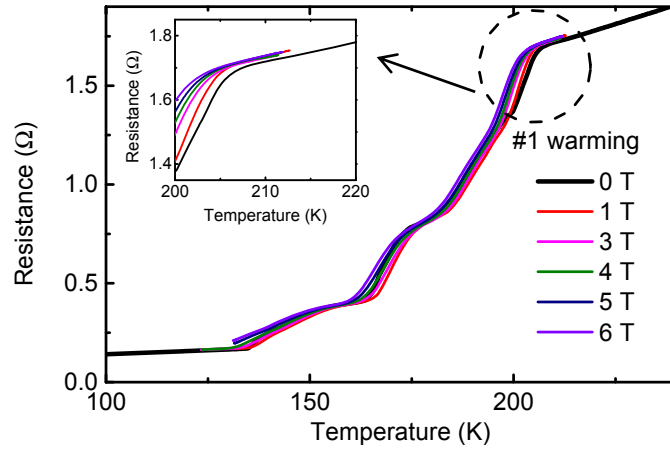


Fig. 2 The resistance as a function of temperature measured at different magnetic field for sample 1. The arrows are attributed to the phases with different hydrogen amount in the calcium superhydrides. The inset is the enlarged view of the resistance curves around the transition region of the 210K phase.

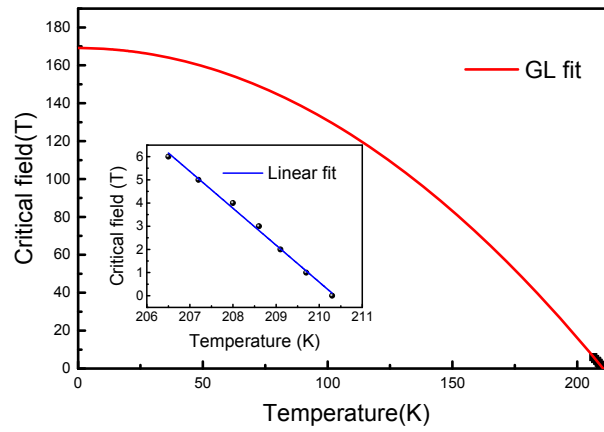


Fig. 3 The temperature dependence of upper critical fields of the 210K phase. The red line is the fit by GL formula with $\mu_0 H_{c2}(0)$ to be 169T. The inset shows the linear fit of the $\mu_0 H_{c2}(T)$.