

Incommensurate Nature of the Antiferromagnetic Order in GdCu₂

Koji Kaneko^{1,2*}, Chihiro Tabata^{1,2}, Masato Hagihala¹, Hiroki Yamauchi¹, Masato Kubota¹,
Toyotaka Osakabe¹, and Yoshichika Ōnuki^{3,4}

¹*Materials Sciences Research Center, Japan Atomic Energy Agency, Tokai, Naka, Ibaraki
319-1195, Japan*

²*Advanced Science Research Center, Japan Atomic Energy Agency, Tokai, Naka, Ibaraki
319-1195, Japan*

³*Faculty of Science, University of the Ryukyus, Nishihara, Okinawa 903-0213, Japan*

⁴*RIKEN Center for Emergent Matter Science, Wako, Saitama 351-0198, Japan*

A magnetic order in orthorhombic GdCu₂ was investigated via a single crystal neutron diffraction with thermal neutron. Magnetic peaks were observed at incommensurate positions described by the ordering vector $\mathbf{q}=(\delta, 1, 0)$ with $\delta=0.678$ at 4.6 K. This ordering vector is close to the commensurate one with $\mathbf{q}_c=(2/3, 1, 0)$ reported earlier, but clearly deviates. The incommensurate nature of the magnetic order in GdCu₂ is further corroborated by the peak shift with temperature below T_N .

Trivalent Gd and divalent Eu ions show unique magnetic properties among rare-earth ions owing to an absence of orbital moment. Intermetallic compounds with Gd³⁺ and Eu²⁺ can be understood as spin magnetism mediated by RKKY interaction. Recently, topological magnetic orders, represented by magnetic skyrmion lattice, were discovered in Eu- and Gd-based compounds.¹⁻⁶ Magnetic skyrmions in *f*-electron systems have characteristic properties such as short periodicity and anisotropy, compared with *d* electron systems, which can result from different formation mechanism.

An orthorhombic compound GdCu₂ attracts renewed interests in this respect. GdCu₂ undergoes an antiferromagnetic transition around 40 K.^{7,8} The magnetic structure in the ground state was reported to be a helical one characterized by the ordering vector $\mathbf{q}_c=(2/3, 1, 0)$.⁹ Because of the strong neutron absorption of Gd, hot neutron, a wavelength of ~ 0.5 Å, was used to minimize attenuation. On the other hand, a short wavelength made it difficult to achieve high resolution in a momentum Q space. In order to get detailed insights into the magnetic

*koji.kaneko@j-parc.jp

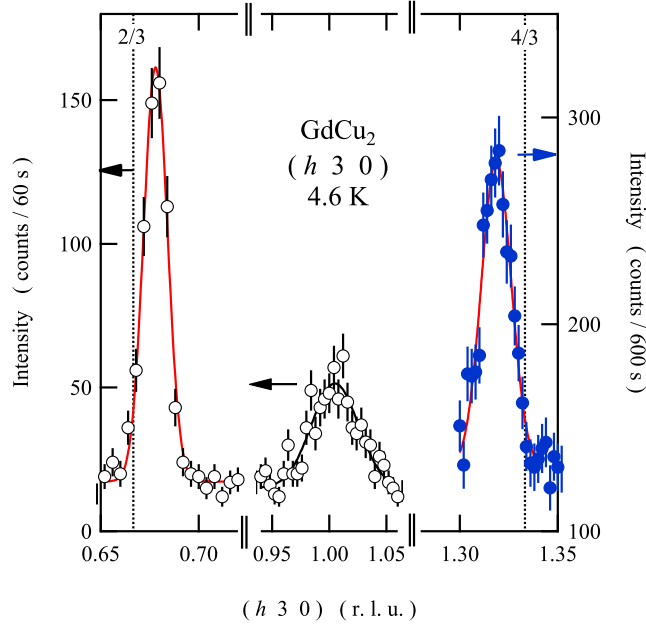


Fig. 1. (Color online) Scan along h through $(1, 3, 0)$ collected at 4.6 K below T_N . Open circles are plotted with the left axis, while the closed circle uses the axis on the right. Dotted lines indicate commensurate peak positions with $\delta=2/3$.

order in GdCu_2 , single crystal neutron diffraction experiment was performed using thermal neutron.

A single crystal sample of GdCu_2 was grown by the Czochralski method as same as in Ref. 8. The plate-like sample of $\sim 4 \times 4 \times 1.8 \text{ mm}^3$ with a plane normal to the b -axis was used in the present study. A single crystal neutron diffraction experiment was carried out on the thermal neutron triple-axis spectrometer TAS-2, installed at the T2-4 beam port in the guide hall of the research reactor JRR-3 in Tokai. Neutrons with a wavelength of 2.359 \AA were obtained and analyzed by pyrolytic graphite (PG) monochromator and analyzer. A collimation set of open- 40° -S- 40° - 80° was employed with a PG filter before the sample. The sample was attached to a cold finger of a closed-cycle refrigerator to have $(h k 0)$ in the horizontal scattering plane.

A linear absorption coefficient for GdCu_2 with natural Gd is enormously large; roughly $9 \mu\text{m}$ thickness will reduce neutron flux down to $1/e$. In order to avoid strong neutron attenuation, reflections close to the reciprocal $(0 k 0)$ axis were chosen to have a reflection geometry for the present sample. Figure 1 shows a scan along h through $(1 3 0)$ measured at 4.6 K below T_N . Three peaks were observed, which consists of a nuclear peak at center at $(1 3 0)$ accompanied by satellite peaks on both sides. Note that the nuclear Bragg peak at $(1 3 0)$ is

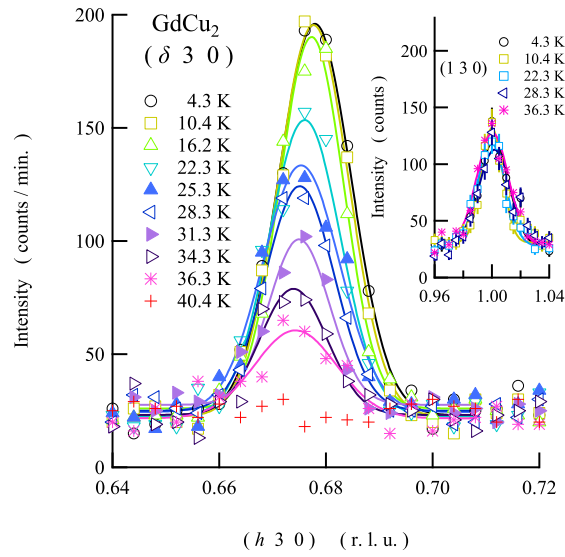


Fig. 2. (Color online) Representative line scan profiles along h through $(\delta 3 0)$ measured at several temperatures below T_N . The inset shows line scan profile through nuclear peak at $(1 3 0)$ recorded at selected temperatures.

forbidden for the symmetry $Imma$. As the central peak serves as a good reference to determine magnetic satellite peak positions precisely, the PG filter was partly removed and use $\lambda/2$ to obtain the peak at $(1 3 0)$. In smaller h region, a sharp magnetic peak was observed at $0.678(1)$ whose width corresponds to expected resolution of ~ 0.013 r. l. u.. In contrast, a subtle, but clear magnetic peak was observed in larger h at $1.323(1)$ plotted in the right axis, which needs 10 times longer counting time to obtain the similar statistics. By using the single parameter δ to fit the both peak positions with respect to the nuclear peak, δ was determined as $0.678(1)$. This is evidently smaller than $2/3$, which is indicated by broken lines in the figure. On the other hand, a scan along k confirms that the magnetic peak is centered at $k=3$, namely the k component is 1. The results indicate that the magnetic order in $GdCu_2$ is not commensurate with $\mathbf{q}_c=(2/3, 1, 0)$, but has an incommensurate nature with $\mathbf{q}=(\delta, 1, 0)$.

This finding is also supported by its temperature dependence. Figure 2 shows the scan along h through $(\delta 3 0)$ collected at several temperatures below T_N . With increasing temperature, the magnetic peak at the incommensurate position at $h=0.678$ becomes weaker, and vanished at 40.4 K just above T_N . Concomitantly, the magnetic peak exhibits gradual peak shift to smaller h as temperature increases. This is contrast to the adjacent nuclear peak $1 3 0$, which stays at the same position as shown in the inset of Fig. 2.

Figure 3 summarizes the temperature variation of the peak position and intensity ob-

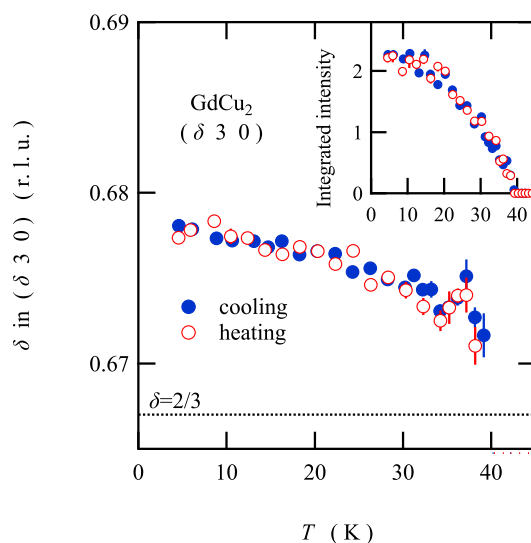


Fig. 3. (Color online) Magnetic peak position δ in $(\delta 3 0)$ as a function of temperature measured upon both heating and cooling. The inset shows temperature variation of the integrated intensity of the same magnetic reflection.

tained by a Gaussian fitting. Concerning the peak position, the peak at 0.678 at 4.6 K exhibits monotonous decrease with the temperature, and becomes 0.671 at 38.2 K. The peak positions δ in the entire temperature range are larger than $2/3$, as indicated by the broken line in the figure. No visible difference exists between upon cooling and heating. A change of the peak position with temperature also supports an incommensurate nature of the transition in GdCu_2 . The magnetic peak intensity shown in the inset develops gradually with decreasing temperature. No visible hysteresis was observed as in the peak position, consistent with a second-order nature of the magnetic transition in GdCu_2 .

The present results reveal the incommensurate nature of the magnetic order in GdCu_2 . The deviation from the commensurate order is small, 0.01 r.l.u. along a . Within the previous magnetic structure model, a small change in periodicity results in a slight reduction in pitch angle; the angle between neighboring magnetic moments along a is reduced from 120° to $\sim 116^\circ$. The lock-in transition to commensurate structure could not be seen in the present temperature range down to 4.6 K.

In general, neutrons with a short wavelength, 1 Å or less, are used to study high neutron absorbing material as absorption cross section follows so-called $1/v$ law, where v corresponds to speed of neutron. Indeed, the high neutron absorption cross section of Gd, 58500 barns at a typical thermal-neutron wavelength 2.36 Å, can be suppressed to roughly 1/100 at hot neutron region at 0.5 Å. This suppression of neutron absorption enables quantitative structure

analysis as in the previous report.⁹⁾ On the other hand, a short wavelength tends to result in a poor resolution in the Q space, in particular for low Q region. In other words, this setup is not ideal to determine precise periodicity as mentioned in Ref. 9. Whereas an accurate absorption correction and structural analysis could be problematic, a peak position and its variation with an external parameter can be tracked accurately with thermal neutron. A complementary use of both short- and long-wavelength neutrons leads to obtain a detailed picture of magnetic order.

In summary, the present study revealed that the antiferromagnetic order in orthorhombic GdCu_2 can be described with the incommensurate ordering vector with $\mathbf{q}=(\delta, 1, 0)$ with $\delta=0.678$ at 4.6 K. The gradual change of δ with the temperature also supports an incommensurate nature of the transition in GdCu_2 .

Acknowledgment

We thank Y. Shimojo and M. Sasaki for their support on neutron scattering experiments. This work was supported by JSPS KAKENHI Grants Nos. JP20H01864, JP21H01027, JP21H04987, and No. JP19H04408.

References

- 1) M. Kakihana, D. Aoki, A. Nakamura, F. Honda, M. Nakashima, Y. Amako, S. Nakamura, T. Sakakibara, M. Hedou, T. Nakama, and Y. Ōnuki, *J. Phys. Soc. Japan* **87**, 023701 (2018).
- 2) K. Kaneko, M. D. Frontzek, M. Matsuda, A. Nakao, K. Munakata, T. Ohhara, M. Kakihana, Y. Haga, M. Hedou, T. Nakama, and Y. Ōnuki, *J. Phys. Soc. Japan* **88**, 013702 (2019).
- 3) M. Hirschberger, T. Nakajima, S. Gao, L. Peng, A. Kikkawa, T. Kurumaji, M. Kriener, Y. Yamasaki, H. Sagayama, H. Nakao, K. Ohishi, K. Kakurai, Y. Taguchi, X. Yu, T.-h. Arima, and Y. Tokura, *Nat. Commun.* **10**, 5831 (2019).
- 4) T. Kurumaji, T. Nakajima, M. Hirschberger, A. Kikkawa, Y. Yamasaki, H. Sagayama, H. Nakao, Y. Taguchi, T.-h. Arima, and Y. Tokura, *Science* **365**, 914 (2019).
- 5) N. D. Khanh, T. Nakajima, X. Yu, S. Gao, K. Shibata, M. Hirschberger, Y. Yamasaki, H. Sagayama, H. Nakao, L. Peng, K. Nakajima, R. Takagi, T.-h. Arima, Y. Tokura, and S. Seki, *Nat. Nanotechnol.* **15**, 444 (2020).
- 6) R. Takagi, N. Matsuyama, V. Ukleev, L. Yu, J. S. White, S. Francoual, J. R. L. Mardegan, S. Hayami, H. Saito, K. Kaneko, K. Ohishi, Y. Ōnuki, T.-h. Arima, Y. Tokura, T. Nakajima, and S. Seki, *Nat. Commun.* **13**, 1472 (2022).
- 7) N. H. Luong, J. Franse, and T. D. Hien, *J. Magn. Magn. Mater.* **50**, 153 (1985).
- 8) A. Koyanagi, Y. Yoshida, Y. Kimura, R. Settai, K. Sugiyama, and Y. Ōnuki, *J. Phys. Soc. Japan* **67**, 2510 (1998).
- 9) M. Rotter, A. Lindbaum, E. Gratz, G. Hilscher, H. Sassik, H. E. Fischer, M. T. Fernandez-Diaz, R. Arons, and E. Seidl, *J. Magn. Magn. Mater.* **214**, 281 (2000).