

Possible canted antiferromagnetism in UCu_9Sn_4

U. Killer^a E.-W. Scheidt^a H. Michor^b J. Hemberger^c H.A. Krug von Nidda^c W. Scherer^a

^a*Chemische Physik und Materialwissenschaften, Universität Augsburg, 86159 Augsburg, Germany*

^b*Institut für Festkörperphysik, TU Wien, 1040 Wien, Austria*

^c*EP V, Elektronische Korrelationen und Magnetismus, Institut für Physik, Universität Augsburg, 86159 Augsburg, Germany*

Abstract

We report on the new compound UCu_9Sn_4 which crystallizes in the tetragonal structure $I4/mcm$ with lattice parameters $a = 8.600\text{\AA}$ and $c = 12.359\text{\AA}$. This compound is isotyp to the ferromagnetic systems RECu_9Sn_4 ($\text{RE} = \text{Ce}, \text{Pr}, \text{Nd}$) with Curie temperatures $T_C = 5.5\text{ K}, 10.5\text{ K}$ and 15 K , respectively. UCu_9Sn_4 exhibits an uncommon magnetic behavior resulting in three different electronic phase transitions. Below 105 K the sample undergoes a valence transition accompanied by an entropy change of $0.5 R \ln 2$. At 32 K a small hump in the specific heat and a flattening out in the susceptibility curve probably indicate the onset of helical spin order. To lower temperatures a second transition to antiferromagnetic ordering occurs which develops a small ferromagnetic contribution on lowering the temperature further. These results are strongly hinting for canted antiferromagnetism in UCu_9Sn_4 .

Key words:

valence transition, canted antiferromagnetism

Recent studies on ternary compounds like CeNi_9Ge_4 [1] and RECu_9Sn_4 ($\text{RE} = \text{Ce}, \text{Pr}, \text{Nd}$) [2] have attracted much interest because of their manifold electronic and magnetic properties. In the non-Fermi liquid (nFL) system CeNi_9Ge_4 we observed the largest ever recorded value of the electronic specific heat $\Delta c/T \approx 5.5\text{ J K}^{-2}\text{mol}^{-1}$ without presence of any trace of magnetic order [1] that is mainly based on single ion effects [3]. Long range ferromagnetic order was found in RECu_9Sn_4 ($\text{RE} = \text{Ce}, \text{Pr}, \text{Nd}$) with Curie temperatures T_C of $5.5\text{ K}, 10.5\text{ K}$ and 15 K , respectively [2]. These systems crystallize in the tetragonal structure $I4/mcm$ with large RE-RE spacings of about 6.1\AA while the corresponding Ce-Ce distances in CeNi_9Ge_4 value at 5.548\AA . In this work we focus on the new isotyp compound UCu_9Sn_4 which is on the borderline between long range magnetic order and nFL behavior due to the expanded 5f-electron orbitals. The X-ray powder pattern of annealed (650°C for one week) polycrys-

talline UCu_9Sn_4 also adopts the tetragonal structure ($I4/mcm$) with $a = 8.600\text{\AA}$ and $c = 12.359\text{\AA}$ which are comparable to the lattice parameters of RECu_9Sn_4 . The *dc*-susceptibility of UCu_9Sn_4 exhibits two pronounced transitions at 105 K and 22 K (Fig. 1). Above 105 K the susceptibility follows a Curie-Weiss law with $\mu_{\text{eff}} = 2.9\mu_B$ which is in between the f^1 and f^2 state of Uranium. The upper transition at 105 K , which is independent of magnetic field, gives rise to a peak in specific heat (Fig. 2). A little anomaly is observed in resistivity measurements as well. The entropy of this anomaly (Fig. 2B) is half of that of an antiferromagnetic transition with effective spin of $1/2$ ($\Delta S = 0.5R \ln 2$) indicating a valence transition from the mixed f^1/f^2 to f^1 state. This is confirmed by the magnetic entropy of $S = R \ln 4$ which is the same as for $\text{Ce } 4f^1$ in CeNi_9Ge_4 . The expected moment of $2.54\mu_B$ is masked by strong magnetic fluctuations below 60 K (see Fig. 2A).

Below 32 K the antiferromagnetic fluctuation tends to long range magnetic order visualized by forming out a shoulder in the susceptibility (arrows in Fig. 1A/B and Fig. 2A). The significant feature in the specific

¹ This work was supported by the SFB 484 of the Deutsche Forschungsgemeinschaft (DFG).

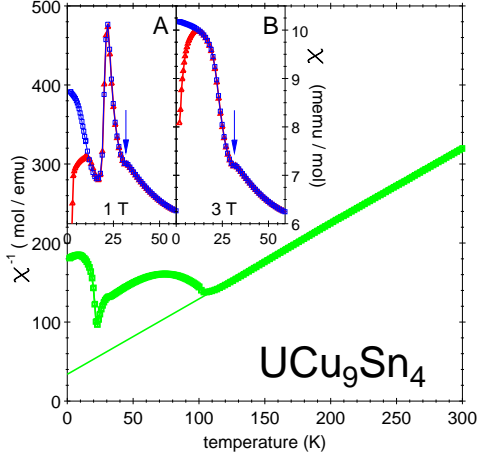


Fig. 1. Inverse magnetic dc susceptibility of UCu_9Sn_4 versus temperature measured in a magnetic field of 0.5 T. The straight line represents a Curie-Weiss fit to the data above 105 K. The insert shows $dc\text{-}\chi$ zero-field (ZFC) / field cooled (FC) splitting in A) $B = 1$ T and B) $B = 3$ T

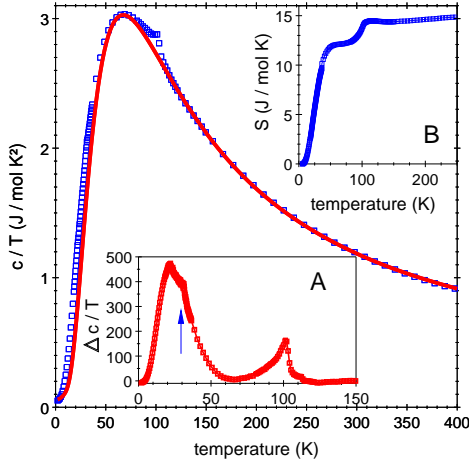


Fig. 2. The specific heat divided by temperature vs. temperature of UCu_9Sn_4 . The solid line is a calculation of the phonon contribution using a Debye and two Einstein terms. A) The electronic contribution to the specific heat $\Delta c/T$. Notice the 3 anomalies at 22 K, 32 K and 105 K. B) The entropy of the magnetic contribution $S = R \ln 4$ per U-mol at 50 K indicates two low lying doublets also found in CeNi_9Ge_4 .

heat and the magnetic field independent transition indicate a helimagnetic phase [4]. On decreasing temperature the sharp peak in the $dc\text{-}\chi$ is characteristic for a second transition into a commensurate antiferromagnetic structure. This is also confirmed by phonon adjusted $\Delta c/T$ data (Fig. 2A) where spin-reorientation is observed at 22 K.

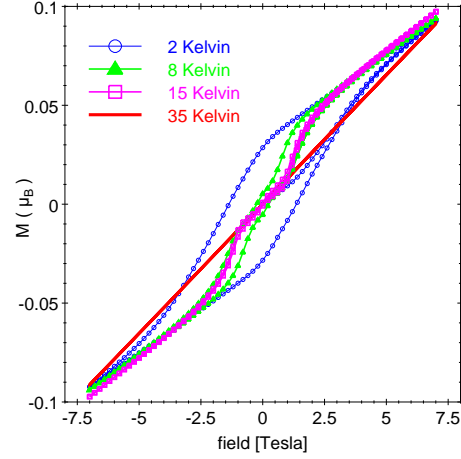


Fig. 3. Metamagnetic behavior and the formation of the canted antiferromagnetic phase below 8 K of UCu_9Sn_4 .

With increasing magnetic field a slight ferromagnetic contribution develops at low temperature indicating a sign of a canted antiferromagnetic state. At high fields (≥ 3 T) a transition from the paramagnetic straight into the canted state occurs already at 32 K (Fig. 1B). In Fig. 3 the magnetic hysteresis corroborates the crossover from pure to canted antiferromagnetism with a spin-flop transition at 15 K and the opening of a hysteresis loop below 8 K with a spontaneous moment of $M_{\text{sat}} \approx 0.03\mu_B$.

The ZFC/FC splitting in $dc\text{-}\chi$ (Fig. 1A/B) may be explained by forming spontaneous small ferromagnetic domains in the canted antiferromagnetic phase below 8 K. In this temperature range the ferromagnetic domains are growing in an external magnetic field. On the occasion of the strong spin-orbit coupling of uranium atoms the domain walls exhibit a large inertia. The absence of any frequency shift of the transition maximum in $ac\text{-}\chi$ measurements rules out frustration effects.

Summarizing three distinguished phase transitions are observed in UCu_9Sn_4 : i) valence shift at 105 K, ii) onset of helimagnetic order at 32 K, and iii) transition into commensurate antiferromagnetic structure at 22 K with magnetic field induced canting.

References

- [1] H. Michor *et al.*, *J. Mag. Mag. Mat.* **272-276**, (2004) 227.
- [2] S. Singh *et al.*, *J. Alloys Comp.* 317-318 (2001) 560-566.
- [3] U. Killer *et al.*, *cond-mat/0402498*.
- [4] J. Hemberger *et al.*, *cond-mat/0311249*.